


## AG 4/8-320

Product : Expanded Clay

Client : Quality Control Argex  
Tel.: +32/32.50.15.08  
Fax: +32/32.50.15.28

Lab	Quality Control Argex Tel.: 0032/32.50.15.08 Fax.: 0032/32.50.15.28
Aggregate Size	4/8 mm
Certifications	CE:EN 13055-1, EN 13055-2 : BSB NL (GR-019/1), KOMO (LT-001/1), ISO 9001:2000
CE:EN 13055-1, EN 13055-2	Lightweight aggregates -Part 1: Lightweight aggregates for concrete, mortar and grout -Part 2: Lightweight aggregates for bituminous mixtures and surface treatments and for unbound and bound applications

TESTS	Minimum	Average	Maximum	Declared	Standard
Particle Shape		Crushed			EN 13055-1
Crushing Resistance (T-2x30")	0.40	1.04 N/mm <sup>2</sup>	2.20		EN 13055-1
Loose Bulk Density	272	327 kg/m <sup>3</sup>	368	320	EN 1097-3
Particle Density	570	681 kg/m <sup>3</sup>	770	670	EN 1097-6
Freezing & Thawing Resistance		3.3 %		4	EN 13055-1
Los Angeles + Micro Deval (4-6.3)		NPD*			EN 1097-1 & 2
Los-Angeles (4-6.3)		NPD*			EN 1097-2
Polished Stone Value		NPD*			EN 1097-8
Volume Stability		0.12 %			EN 13055-1
Water Content	0.0	3.1 %	100.0		EN 1097-5
Water Absorption (5')	18.00	27.37 %	50.00		EN 1097-6
Water Absorption (30')	22.00	31.23 %	52.00		EN 1097-6
Water Absorption (24h)	37.00	47.25 %	65.00		EN 1097-6
Alkali Silica Reactivity		Not Relevant			EN 13055-1
Chemical Analysis Argex		100.00 %			
SiO <sub>2</sub>	55	59.50 %	65		
Mn <sub>2</sub> O <sub>3</sub>	0.15	0.20 %	0.25		
K <sub>2</sub> O	1.5	3.00 %	3.5		
TiO <sub>2</sub>	0.8	0.90 %	1		
MgO	1	1.50 %	2		
S	0.7	1.00 %	1.3		
Al <sub>2</sub> O <sub>3</sub>	15	17.00 %	19		
Na <sub>2</sub> O	0.3	0.50 %	0.7		
Fe <sub>2</sub> O <sub>3</sub>	12	14.30 %	16		
P <sub>2</sub> O <sub>5</sub>	0.05	0.10 %	0.15		
CaO	1	2.00 %	3		
Chloride		0.005 %		0.02	EN 1744-1
Cleanliness		OK			EN 1744-1
Emission Of Radioactivity		NPD*			EN 13055-1
Loss on Ignition		-0.18 %		5	EN 1744-1
Release Of Heavy Metals		NPD*			EN 13055-1
Release Of Other Dangerous Substances		NPD*			EN 13055-1
Release Of Polyaromatic Carbons		NPD*			EN 13055-1
Reaction To Fire		A1			EN 13501-1
Total Sulphur		0.594 %		0.8	EN 1744-1
Acid-Soluble Sulfate		0.078 %		0.8	EN 1744-1

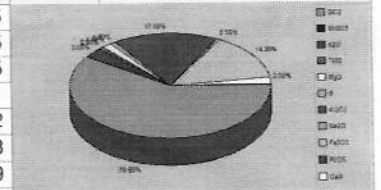

NPD\* = No Performance Determined



CE 2008  
0965-CPD-GT0525  
0965

**ARGEX NV**  
Kruibeeksesteenweg 227-229  
B-2070 Burcht-Zwijndrecht  
BELGIUM

**Technical Sheet**  
du 1/01/2007 to 31/12/2007

Page 2/2


## AG 4/8-320

**Product :** Expanded Clay

**Client :** Quality Control Argex  
Tel.: +32/32.50.15.08  
Fax: +32/32.50.15.28

<b>Lab</b>	Quality Control Argex Tel.: 0032/32.50.15.08 Fax.: 0032/32.50.15.28
<b>Aggregate Size</b>	4/8 mm
<b>Certifications</b>	CE:EN 13055-1, EN 13055-2 : BSB NL (GR-019/1), KOMO (LT-001/1), ISO 9001:2000
<b>CE:EN 13055-1, EN 13055-2</b>	Lightweight aggregates -Part 1: Lightweight aggregates for concrete, mortar and grout -Part 2: Lightweight aggregates for bituminous mixtures and surface treatments and for unbound and bound applications

Grading (Standard EN 933-1)				
Mass Sieve (mm)	Minimum	% passing	Maximum	Declared
0.000		0.0	0.0	
0.063			1.4	
2.000		0.0	3.7	
3.150		0.0	5.7	
4.000		0.0	10.0	15.0
6.300			67	
8.000		90	97	100
10.000		96	100	100

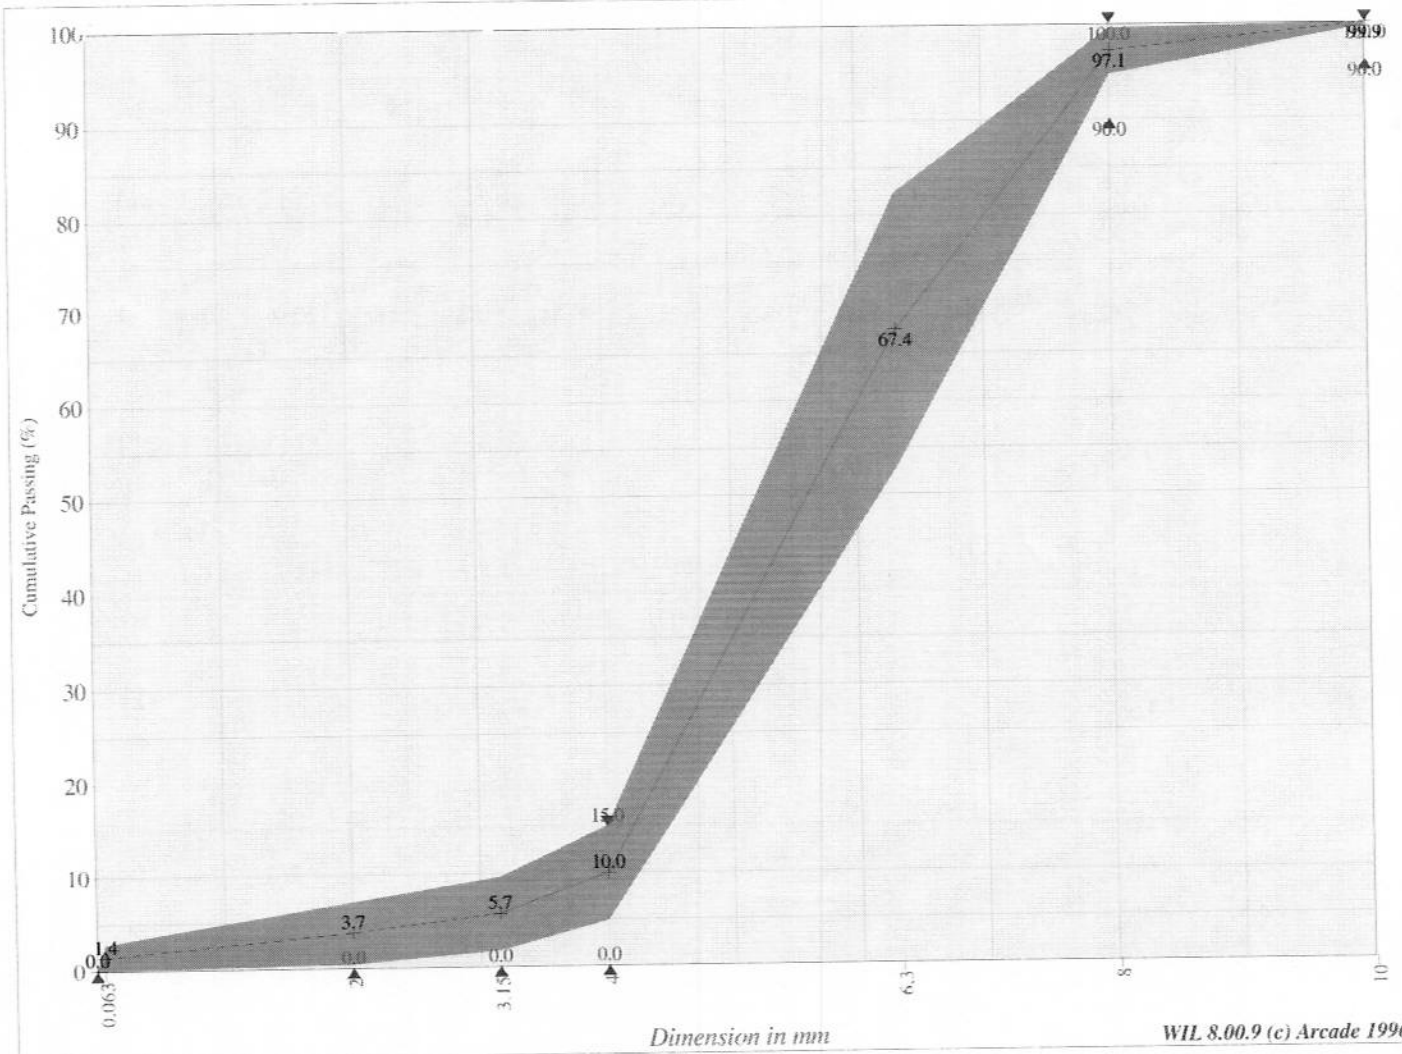

WIL 8.00.9 (c) Arcade 1996,2007

NPD\* = No Performance Determined